

INFLUENCE OF WELDING PHYSICAL CONDITIONS ON WATERPROOFING MEMBRANE WELD QUALITY

Michal Bucko, Sergej Hloch, Jan Valíček, Hakan Tozan, Yashar Javadi, Aniruddha Ghosh

Preliminary notes

The paper deals with the influence of factors on the welding of waterproofing membranes in order to achieve the technological process rationalization. The influence of factors (speed, temperature, and welding time) upon waterproofing membrane weld quality was assessed through an experiment. The most suitable factor combinations were determined with the aim to ensure the welds of the highest quality. Thus a tool for the less experienced welders was generated by means of which the period of an operator's training shall be reduced.

Keywords: *waterproofing membrane, welding*

Utjecaj fizikalnih uvjeta zavarivanja na kvalitetu zavarenog spoja vodonepropusne membrane

Prethodno priopćenje

Članak se bavi utjecajem čimbenika na zavarivanje vodonepropusnih membrana u cilju postizanja racionalizacije tehnološkog procesa. Utjecaj čimbenika (brzine, temperature i vremena zavarivanja) na kvalitetu zavora vodonepropusne membrane ocijenjen je eksperimentom. Utvrđene su najprikladnije kombinacije faktora s ciljem osiguranja zavora najviše kvalitete. Tako je za manje iskusne zavarivače razvijen alat pomoću kojega će razdoblje osposobljavanja zavarivača biti smanjeno.

Ključne riječi: *vodonepropusna membrana, zavarivanje*

1

Introduction

Nowadays, due to their numerous favourable properties, plastic materials replace other materials in many industries, especially packaging industry, therefore the generation of plastic waste is constantly increasing [1-13]. Remarkable growth of flat roof insulation commenced in the 1970s of the last century. A flat roof is a roof with a slope up to 15°. Initially the flat roofs were insulated using melting bituminous asphalt strips. Insulations were realized through a free flame in case of which an asphalt strip was preheated and adhered to a prepared roof base. Their drawback was in short durability. The welded PVC films were preceded by the adhered ones joined by adhesives [1], [7]. Due to unsatisfactory experience related to adhesives changing their properties after some time and occurrence of opening of joints the film strips began to be welded. At present the films are recommended to be merely welded [14, 15, 16]. Films are welded using automatic welding machines and manual hot air guns in contrast to bitumen being melted down manually by free flame. Material and work guarantee significantly differ. In case of bituminous strips the period ranges from approximately 2 to 3 years whereas film guarantee is minimally 10 years.

2

State of the art

Currently, according to the available data, both in Slovakia and the Czech Republic, to insulate roofs and basement complexes of large shopping centres in construction so as to prevent water, humidity and radon PVC films are used by diverse world producers including Fatra, Carbofol, Sika, Juta, Agru, Flagon. Trainings of PVC film welders lasting usually 1 week are held in Slovakia within the frame of material producers or suppliers. They are organized annually or every other year. It is a rather

short period of time to train a welder for practice. Information is passed on within the scope of companies in the form of welders' skills being proved in practice. Nowadays no tabular values exist to weld PVC material. Producers provide solely rough temperature ranges in machine set-up according to welded film thickness. Roof insulation guarantee periods apply generally to 10 years. Insulation group normally consists of four to seven people two of whom are experienced welders capable of handling and setting optimal parameters to ensure welding by means of automatic welding machine or manual welding machines. The objective of my work is to model miscellaneous welding parameters and to detect tensile forces of individual samples. In this way I would like to establish a tool for the PVC film welders – a table containing the values the parameters of which ensure the most solid weld. Thus the welding work quality is assured to the utmost. Eventual claims concerning leakages of roofs and basement complexes are eliminated to the largest extent, as repairs are financially demanding. The claims lie in damaged insulation replacement, drying and renovation of destroyed interiors under insulated covering (wall drying, decoration, floor and furniture recovery, etc.). One of the most significant welding conditions is to provide both clean instruments of welding elements and welded areas, too. Active areas of hot bodies as well as tools and instruments and areas being joined are inevitable to be thoroughly cleaned. Usage of textile material for cleaning is unsuitable therefore many times paper not giving off fibres – toilet-paper is applicable - and pure cleaning agent-free water are used [4, 16, 17, 18, 19, 20]. Film thickness depending on type of use and material supplier may be selected in the range from 1,00 mm up to 2,00 mm. Roof utilization intended film is UV stable and reinforced by fibres preventing shrinking. In dependence on a producer material guarantee is minimally 10 years. Film strip width ranges from 1,2 to 2,0 metres. Recommended thickness in case of roof insulation is minimally 1,5 mm adhering to 10-

year guarantee period. To insulate basement complexes PVC films with thickness ranging from 1,2 to 2,0 metres are used. In general those are not UV stable. In covering beads the weld covering is to be of minimum 10 cm. Width of the weld must be 3 cm at least [1]. External ambient conditions influence both assembly period and savings of assembling companies. Under correct optimization of welding processes, observing qualitative and quantitative parameters, welding company can achieve significant savings. Air humidity measurement is to be monitored when welding. High concentration of water vapour results in a dew point formation. The dew point temperature changes depending on outside temperature and relative air humidity [15, 16]. Effects of external ambience and their countermeasures are given in Tab. 1.

Table 1 Conditions and effects for film welding and countermeasures

| Environmental conditions | Impact on welding | Countermeasures |
|--|---|---|
| Rainfall | Faulty welds, it is not possible to weld | Build a protective tent to prevent water intrusion |
| High humidity Must not exceed 80 % | Condensate, particularly related to the low temperatures | Immediately prior to welding preheat welding zone and dry areas |
| Low temperatures (<5 °C) | Condensate formation, changed welding conditions of condensate | Preheat the welded area at 10÷15 °C. Use plant protective tent (if available) |
| High temperatures | Inadmissible dimensional changes, high thermal expansion | Adaptation conditions |
| Direct sunlight | Unequal thermal expansion, changes in dimensions and shapes | Protect by covering |
| Wind, Draught | Increased irregular thermal expansion, unequal and irregular welding temperature. Insufficient plastification welding zone. Impurities in weld area (soot dust) | Shading walls (tent) |
| Chimney effect in the pipes | Improper cooling, heating and welding tools for welding areas | Conclude non-welded ends of a pipe welding |
| Different temperatures of welded parts | Increased irregular thermal expansion. Uneven welding temperature. Inadequate and irregular plastification welding | Tempering material for a sufficiently long period prior to welding |

3 Material and methods

During experiments the FATRAFOL brand PVC film of 1,5 mm thickness was used. Different welding speeds, temperature and amount of exhaust air were selected

according to empirical practice of the operator. In order to investigate strength of welded joints of PVC material with dimension 25×170 mm were prepared according to experimental conditions listed in Tab. 2. Samples were welded by compact and handy welding machine Tarpon by Herz GmbH Company. All destructive tests were conducted on tensile test machine WPM Thuringer Industriewerk Rauenstein 2 kN. All experimental runs were performed on laboratory room with temperature 20 °C.

Table 2 Experimental conditions (3 factors, 1 block, 35 runs)

| Runs | Temperature / °C | Speed / m/min | Air / % | Exfoliation (Peel Strength) / N |
|------|------------------|---------------|---------|---------------------------------|
| 1 | 400 | 1,5 | 100 | 60 |
| 2 | 400 | 2,0 | 100 | 40 |
| 3 | 400 | 2,5 | 100 | 35 |
| 4 | 400 | 3,0 | 100 | 20 |
| 5 | 450 | 1,5 | 100 | 130 |
| 6 | 450 | 2,0 | 100 | 95 |
| 7 | 450 | 2,5 | 100 | 65 |
| 8 | 450 | 3,0 | 100 | 35 |
| 9 | 500 | 1,5 | 100 | 155 |
| 10 | 500 | 2,0 | 100 | 120 |
| 11 | 500 | 2,5 | 100 | 110 |
| 12 | 500 | 3,0 | 100 | 65 |
| 13 | 550 | 1,5 | 100 | 115 |
| 14 | 550 | 2,0 | 100 | 135 |
| 15 | 550 | 2,5 | 100 | 140 |
| 16 | 550 | 3,0 | 100 | 110 |
| 17 | 400 | 1,5 | 80 | 70 |
| 18 | 400 | 2,0 | 80 | 42 |
| 19 | 400 | 2,5 | 80 | 18 |
| 20 | 400 | 3,0 | 80 | 10 |
| 21 | 450 | 1,5 | 80 | 125 |
| 22 | 450 | 2,0 | 80 | 85 |
| 23 | 450 | 2,5 | 80 | 45 |
| 24 | 450 | 3,0 | 80 | 25 |
| 25 | 500 | 1,5 | 80 | 151 |
| 26 | 500 | 2,0 | 80 | 108 |
| 27 | 500 | 2,5 | 80 | 80 |
| 28 | 500 | 3,0 | 80 | 55 |
| 29 | 550 | 1,5 | 80 | 132 |
| 30 | 550 | 2,0 | 80 | 150 |
| 31 | 550 | 2,5 | 80 | 120 |
| 32 | 550 | 3,0 | 80 | 100 |
| 33 | 600 | 2,0 | 100 | 75 |
| 34 | 600 | 2,5 | 100 | 105 |
| 35 | 600 | 3,0 | 100 | 105 |

Destructive assembling tests – tensile tests and tests by a "peel test" are carried out prior to welding and in case of any change of climatic factors (humidity, temperature, wind, etc.) which might influence welding temperature itself. The cooled weld is tested through tearing the upper strip off the lower one. When achieving the continuous weld the welding machine set-up is satisfactory along the entire width. The strip with width of approximately 25 mm and length of 170 mm is to be cut off the randomly selected weld and used to check the weld quality by destructive method (Fig. 2). Film welding quality is high if the film gets torn out of the weld area during destructive test. Visual weld check – all welds are

to be visually checked after completing the welding [1, 9, 18].

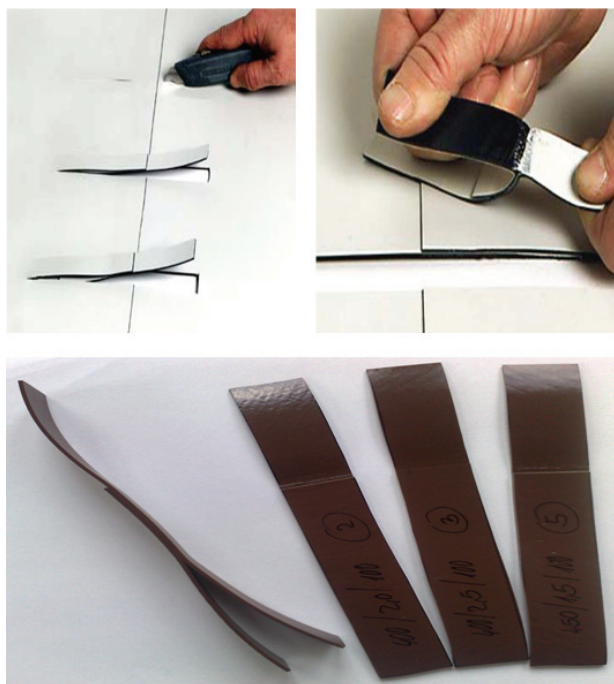


Figure 1 Samples



Figure 2 Tensile test

4

Results and discussion

In the tensile tests performed using a tensile machine no destruction in the welded joint of any sample was observed. Therefore we excluded the samples tested by this method out of further research. We focused on the peeling test results. Foreign literature uses also the term peel test [1]. In consideration of the measured values and after consultation with the welders of the Pastel Company we determined suitable samples showing peeling force from 100 N upwards. The results were used to construct a strength range curve of the most suitable values acquired in welding the experimental samples (Fig. 2). The results were analysed by Statistica 8, using the analysis of variance as appropriate to the experimental design used (Central Composite Experiments). The regression equation obtained after analysis of variance gives the level of average roughness as a function of independent

variables listed in Tab. 1. Significant (Fig. 3) terms are included in the following equation 1:

$$Exf = 107,48 + 18,83 \cdot T - 8,97 \cdot T^2 - 27,75 \cdot S. \quad (1)$$

The fit of the regression model is expressed by coefficient of determination $R^2 = 0,8979$ which was found to be for equation indicating that 89,79 % for the model of the variability in the response can be explained by derived Eq. (1). This shows that equation is suitable model for describing to the response of the exfoliation. The value of adjusted coefficient of determination $adj = 0,8735$ is high to advocate for a high significance of the regression Eq. (1).

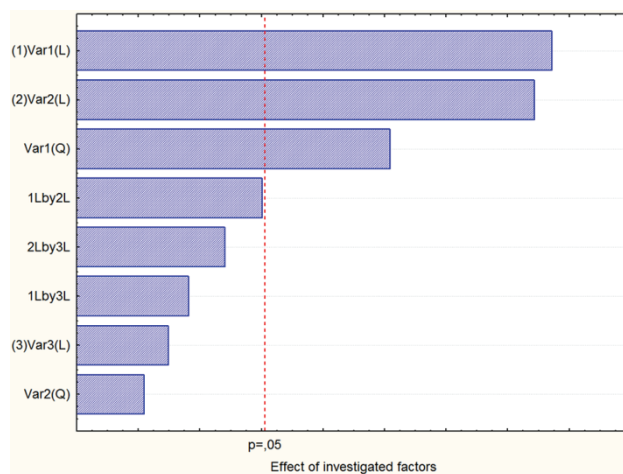


Figure 3 Pareto chart shows that temperature and welding speed as a controllable factor were found to be the most sufficient factors that affect the Exfoliation (N)

The significance of independent variables is interpreted in the Pareto chart of standardized effects for variable Exfoliation (N) (Fig. 3). The following Fig. 4 shows fitted surface of speed and temperature. To construct strength curves speed parameters of the welding machine TARPON by the HERZ Company were opted for the horizontal axis. The vertical axis shows peel force data detected in case of the tensile machine FM 1000. Strength range data were limited through welding parameters having been proved to be the optimal. In this case it was the temperature, the samples were welded at, and amount of additional hot air. Data displayed on the automatic welding machine being digitally set up to 100 % represent the value of 500 l/min of the air. Data 80 % represents the value of 400 l/min of the hot air. As to strength the samples with welding temperature range from 450 °C to 600 °C were the most suitable (Fig. 5). The samples welded at 450 °C possessed almost identical results with the amount of air reaching 100 % or 80 %. Welding at such temperature requires a short range of welding speed. Welding at the foregoing temperatures is recommended to the professional welders only. The strength curve shows rapid drop in strength of the welded joint even in case of slight speed increase of welding. As per welders' experience such temperature parameters are advisable to be preset only if the ambient air temperature reaches over 28 °C.

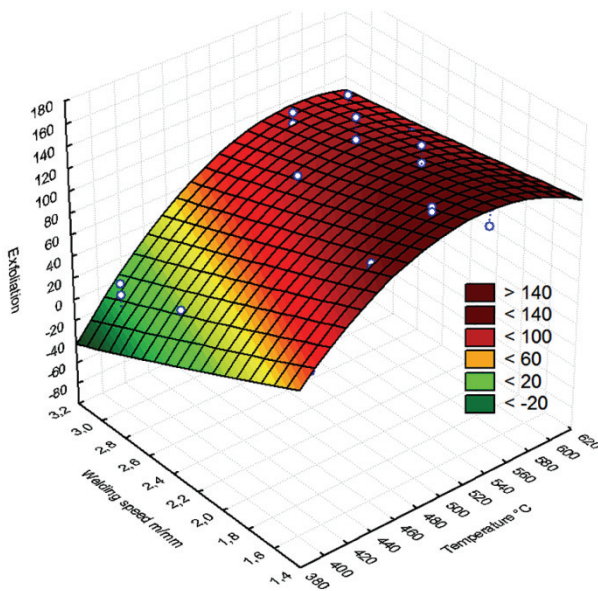


Figure 4 Fitted surface of welding speed and temperature. Three-dimensional surface plot showing predicted value (Exfoliation) as a function of temperature and speed (Tab. 1)

A very interesting phenomenon occurred when the automatic welding temperature was increased to 600 °C. Strength of joints did not increase. Yet rather high film smoking at the point of the weld could be observed during welding. We assume that at these temperatures additional filling agents (additives) were being burnt on the welded film. This may be a cause of relatively low strength of the welds. Welding at these temperatures is recommended if the ambient temperature drops below 10 °C or under unfavourable wind conditions bringing about cooling of the welds. Such welding temperatures might be coped with by the professional welder only.

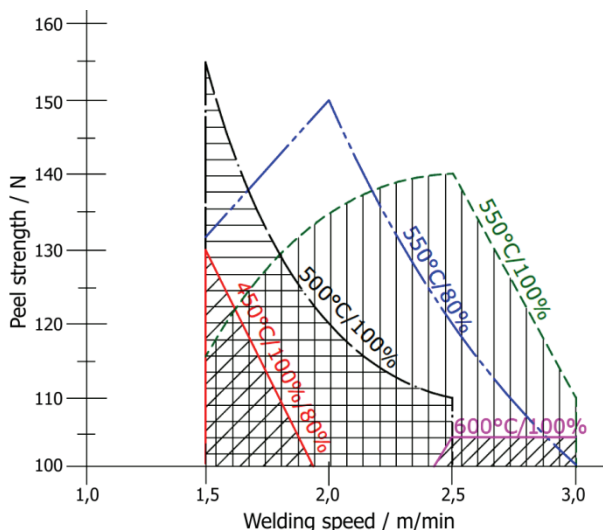


Figure 5 Ranges of strength of welded joints of PVC material, depending on temperature, amount of additional air and welding machine speed

Temperatures around 550 °C ensure optimal welding zone for even less experienced welders. Range of 100 % air is advisable in case of lower ambient temperatures from 5 °C to 20 °C and selection of range of 80 % air is recommended at ambient temperature ranging from 20 °C upwards. At these temperatures a relatively high possibility exists of welding speed selection and

achievement of a good result in case of the welded joint. The measured results very clearly show welding zones with positively strong welded joint of high quality.

5

Conclusion and remarks

In this work, we focused on quality evaluation of the welding parameters of waterproofing membrane in order to achieve the highest quality of the welded joints. Evaluate were tensile parameters of welded samples according to experimental design following factors speed, temperature, and welding time were employed in this study. A design of experiments was used for investigation of significance employed factors. Temperature and welding speed as controllable factors were found to be the most sufficient factors that affect the parameter – Exfoliation. Derived regression equation predicts the behaviour of the quality parameter. It has a significant impact on economy and companies. We believe that the data obtained will serve as a credible figure for the current and future welders.

Acknowledgement

Experiments were carried out under the project support science and research VEGA 1/0972/11.

6

References

- [1] Hessel, J. Obmann der AGW 4: Taschenbuch : Die Merkblätter und – Richtlinien Fugen von Kunststoffen, Düsseldorf, 2008, 880.
- [2] Pilipović, A.; Raos, P.; Šercer, M. Experimental testing of quality of polymer parts produced by laminated object manufacturing - LOM. // Tehnički vjesnik - Technical Gazette, 18, 2(2011), pp. 253-260.
- [3] Monkova, K.; Monka, P. Modelling of complex-shaped components in the scope of reverse engineering. Annals of DAAAM for 2008 & Proceedings of the 19th International DAAAM Symposium, (2008), pp. 903-904.
- [4] Stark TD, Pazmino LF. High-temperature air channel testing of thermally bonded PVC geomembrane seams. // Geosynthetics International, 18, 2(2009), pp. 84-89.
- [5] Jayabal, S.; Natarajan, U.; Sekar, U. Regression modeling and optimization of machinability behavior of glass-coir-polyester hybrid composite using factorial design methodology. // Int. J. Adv. Manuf. Technol., 55, 1-4(2011), pp. 263-73.
- [6] Jurić, A.; Štefić, T.; Arbanas, Z. Experimental analysis of the strength of a polymer produced from recycled material. // Tehnički vjesnik - Technical Gazette, 18, 4(2011), pp. 627-631.
- [7] Knapčiková, L.; Herzog, M.; Oravec, P. Material characterization of composite materials from used tires. // Manufacturing engineering - Výrobné inžinierstvo, 4(2010), pp. 31-34.
- [8] Stark, T. D.; Choi, H.; Thomas, R. W. Low-temperature air channel testing of thermally bonded PVC geomembrane seams. // Geosynthetics International, 11, 6(2004), pp. 481-490.
- [9] Van De Ven, J. D.; Erdman, A. G. Hot pin welding of thin poly(vinyl chloride) sheet. // Journal of Vinyl and Additive Technology, 13, 2(2007), pp. 110-115.
- [10] Bates, I.; Zjakić, I.; Milković, M. Lightfastness and weatherfastness of overprint pattern obtained on polymer

- substrates. // Tehnički vjesnik - Technical Gazette, 18, 3(2011), pp. 349-56.
- [11] Štefić, T.; Jurić, A.; Marović, P. Determination of modulus of elasticity for glass fibre reinforced polymers. // Tehnički vjesnik - Technical Gazette, 18, 1(2011), pp. 69-72.
- [12] Mikoč, M.; Bjelobrk, I.; Korajac, J. Alkali-activated fly ash concrete (concrete without cement). // Tehnički vjesnik - Technical Gazette, 18, 1(2011), pp. 99-102.
- [13] Ogrizovic, M.; Dudukovic, G. The technique of quick designing of casting panel for plastic gear wheel injection. Tehnički vjesnik - Technical Gazette, 17, 2(2010), pp. 251-254.
- [14] Pilipović, A.; Bakić, A.; Rujnić-Sokele, M. Influence of crosslinking parameters on the quality of rubber product. Tehnički vjesnik - Technical Gazette, 17, 2(2010), pp. 185-90.
- [15] Knapčíková, L. Studying the surface of thermoplastics using atomic force by microscopy. // Plastics, 5, 1(2010), p. 30.
- [16] Bedeković, G.; Salope, B.; Sobota, I. Electrostatic separation of PET/PVC mixture. // Tehnički vjesnik - Technical Gazette, 18, 2(2011), pp. 261-266.
- [17] Thomas, R. W.; Stark, T. D. Reduction of destructive tests for PVC seams. // Geotechnical Fabrics Report, 21, 2(2003), pp. 26-29.
- [18] Stokes, V. K. Hot-tool and vibration welding of poly(vinyl chloride). // Journal of Vinyl and Additive Technology, 6, 3(2000), pp. 158-165.
- [19] Mitelea, I.; Varzaru, N.; Bordeasu, I.; Popescu, M. The high frequency welding aptitude of thermoplastic polymers. // Materiale Plastice, 46, 1(2009), pp. 101-107.
- [20] Mitelea, I.; Varzaru, N.; Bordeasu, I.; Scurtu, D. Failure analysis of high frequency welding fixed joints of thermoplastic polymers. // Materiale Plastice, 46, 4(2009), pp. 439-443.

Authors' addresses

Michal Bucko

Faculty of Manufacturing Technologies
of Technical University of Košice with a seat in Prešov
Štúrova 31 080 01 Prešov
Slovak Republic

Sergej Hloch

Faculty of Manufacturing Technologies
of Technical University of Košice with a seat in Prešov
Bayerova 1 080 01 Prešov
Slovak Republic

Jan Valíček

Institute of Geonics Academy of Science
Studentská 1768/9
708 00 Ostrava-Poruba
Czech Republic

Hakan Tozan

Department of Industrial Engineering
Turkish Naval Academy
34942 Tuzla / Istanbul
Turkey

Yashar Javadi

Faculty Member, Islamic Azad University - Semnan Branch
Semnan
Iran
yashar_javadi@yahoo.com

Aniruddha Ghosh

Mechanical Engineering
Govt. College of Engg. & Textile Technology
Berhampore, WB
India